



DW-308L

**Classification: AWS A5.22 E308LT0-1
AWS A5.22 E308LT0-4**

All-Weld-Metal (100%CO₂)

1-1. Chemical Composition



[Unit: mass%]

	C	Mn	Si	P	S	Ni	Cr	N
DW-308L	0.02	1.29	0.44	0.017	0.010	9.88	19.16	0.014
E308LT0-X	<0.04	0.5~2.5	<1.0	<0.04	<0.03	9.0~11.0	18.0~21.0	-----
	WRC ₋₁₉₉₂ (FN)		Shaeffler Diagram (%)		Delong Diagram (FN)			
DW-308L	9.2		7.8		10.2			
E308LT0-X	-----		-----		-----			


1-2. Tensile Test

	0.2% Proof stress (psi)	Tensile strength (psi)	Elongation (%)	Reduction of Area (%)
DW-308L	61,132	78,898	42	47
E308LT0-X	---	>75,000	>35	---

Note) Test was completed in the as welded condition and at room temperature

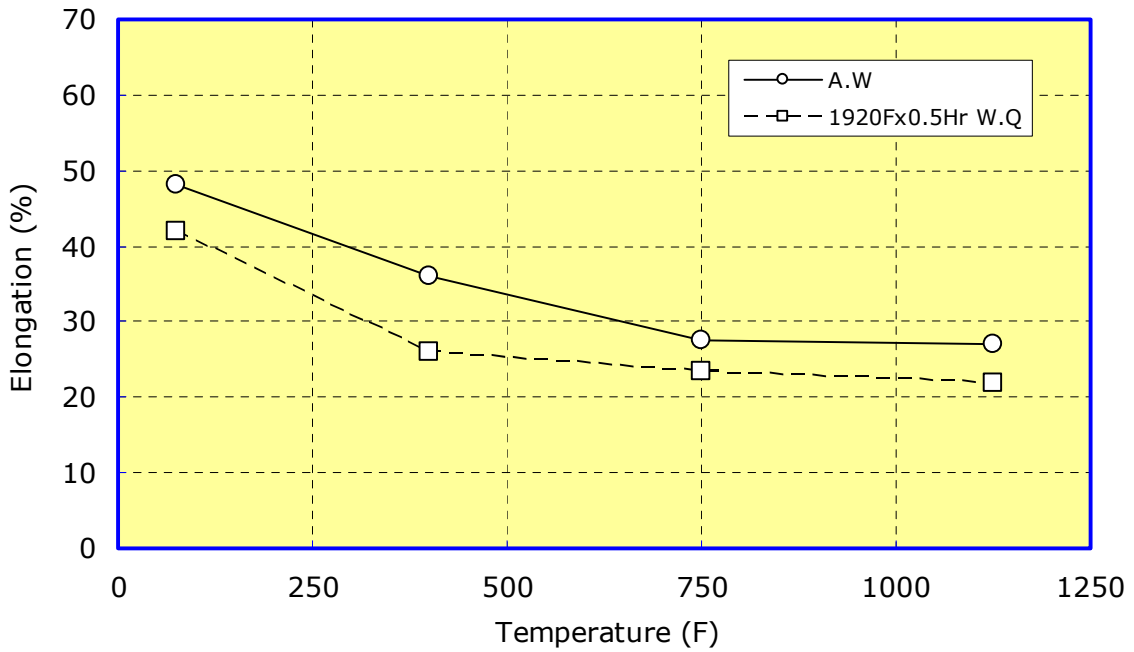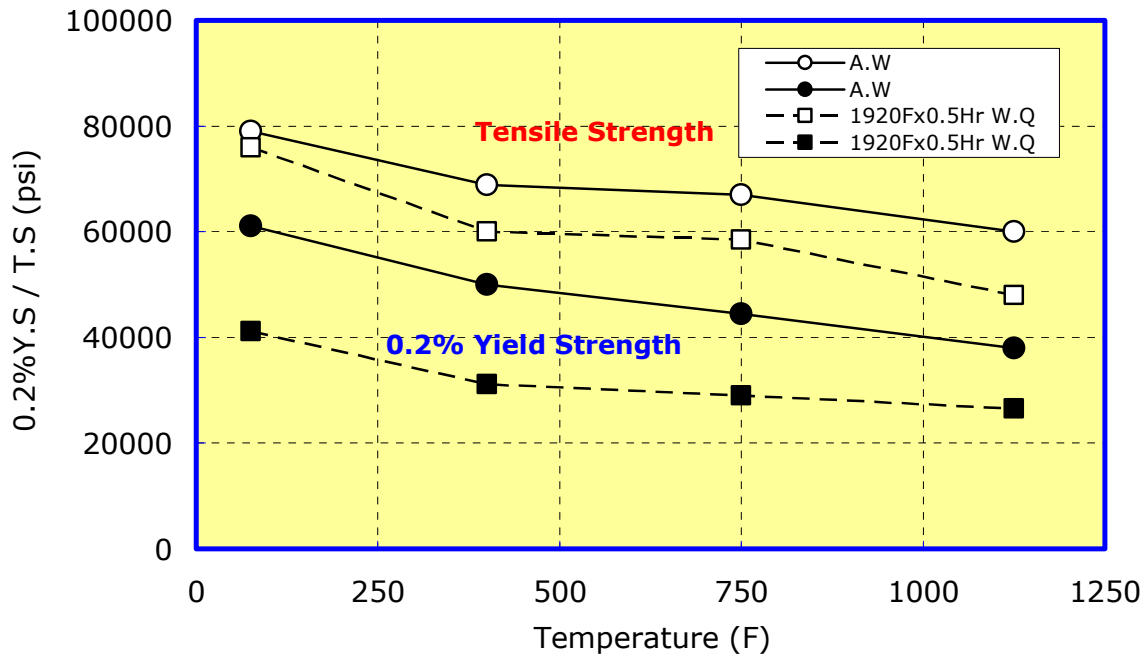

1-3. Impact Test

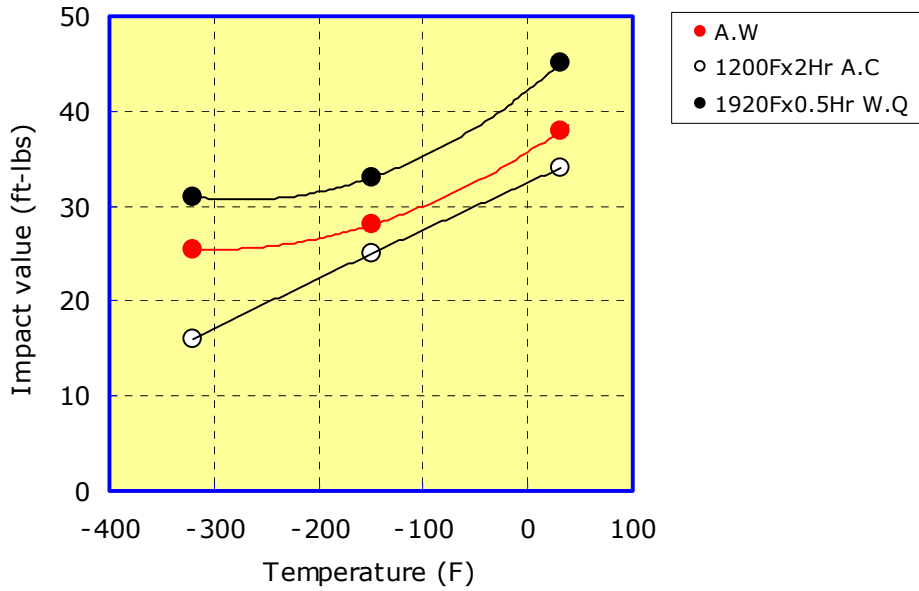

1-4. Corrosion Test

PWHT	Test results (IPM)			
	1 st	2 nd	3 rd	Ave.
As Welded	0.00059	0.00065	0.00054	0.00059
1200° F - 2hr *	0.00081	0.00097	0.00101	0.00093
1920° F - 0.5hr **	0.00042	0.00045	0.00045	0.00044

* Air cooled

** Water quenched

Huey Test (65% Nitric Acid Test)

Welding Journal, Oct. 1951 "Corrosion Data of Welding Low Carbon Stainless Steel"

Excellent < 0.0009 IPM

Good < 0.0009 – 0.0021 IPM

Fair < 0.0021 – 0.0042 IPM

Poor > 0.0042 IPM

Copper sulfuric acid test

PWHT : 1200° F x 2Hr A.C

Bend test results : No defect